

OFFICE OF NAVAL RESEARCH

CONTRACT N00014-89-J-1145

R&T Code 413m011

Program Manager Dr. K. Wynne

Technical Report No. 35

AD-A281 216



Characterization of the One Step Polyimide Synthesis


by

G. Jen, S.J. Huang and C.S.P. Sung

Prepared for Publication

in the

ACS Proceedings of Polymer Materials
Science and Engineering

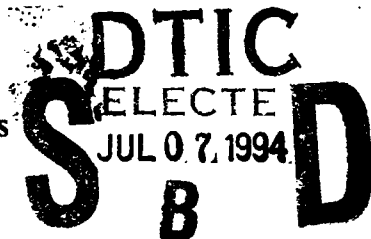

Institute of Materials Science
University of Connecticut
Storrs, CT 06269-3136

June 1, 1994

Reproduction in whole or in part is permitted for any purpose of the United States
Government

This document has been approved for public release and sale;
its distribution is unlimited.

DTIC QUALITY INSPECTED 3

94-20521



496

94 7 6 015

Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204 Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188) Washington, DC 20503.

1. AGENCY USE ONLY (Leave blank)		2. REPORT DATE June 1, 1994		3. REPORT TYPE AND DATES COVERED Technical 6/93 - 5/94	
4. TITLE AND SUBTITLE Characterization of the One Step Polyimide Synthesis				5. FUNDING NUMBERS NR 413M011 N00014-89-J-1145	
6. AUTHOR(S) G. Jen, S.J. Huang and C.S.P. Sung					
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) Institute of Materials Science 97 North Eaglevill Rd. University of Connecticut Storrs, CT 06269-3136				8. PERFORMING ORGANIZATION REPORT NUMBER Technical report No. 35	
9. SPONSORING / MONITORING AGENCY NAME(S) AND ADDRESS(ES) ONR 800 North Quincy Ave Arlington, VA 22217				10. SPONSORING / MONITORING AGENCY REPORT NUMBER	
11. SUPPLEMENTARY NOTES Published in ACS Proceedings of Polymer Materials Science and Engineering, <u>69</u> , 453, 1993					
12a. DISTRIBUTION / AVAILABILITY STATEMENT Reproduction in whole or in part is permitted for any purpose of the United States Government. This document has been approved for public release and sale; its distribution is unlimited.				12b. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 words) The one step high temperature reaction of 3,3',4,4'-benzophenone tetracarboxylic dianhydride (BTDA) and 1,5-naphthyl diamine (DAN) in <i>m</i> -cresol was investigated using UV-Visible, fluorescence, and Infrared spectroscopy. Results have shown that UV-Visible can be used to monitor the wavelength shift from the diamine to the polyamic acid to the polyimide. Deconvolution of the spectra at various reaction times revealed the composition of amic acid and imide, which were also in good agreement with the Infrared analysis. Fluorescence spectroscopy utilized the fluorescence nature of the diamine to probe the reactivity of the species during the reaction. Early complexation of the diamine was evidenced by the absence of fluorescence emission due to DAN, which then appeared later in time to a maximum of 9.4%. Upon further reaction, DAN is consumed completely, as evidenced by the gradual decline in emission. Investigation of this reaction in NMP with only 10% <i>m</i> -cresol at lower temperatures revealed that the apparent rate constants of amic acid formation was actually slower than the controls, 100% NMP as determined by Infrared. However, these laced systems did induce imidization at the lower temperatures.					
14. SUBJECT TERMS One-step polyimide synthesis, UV-visible, Fluorescence and FT-IR spectroscopy, high temperature reaction in <i>m</i> -cresol.				15. NUMBER OF PAGES 2	
				16. PRICE CODE	
17. SECURITY CLASSIFICATION OF REPORT	18. SECURITY CLASSIFICATION OF THIS PAGE	19. SECURITY CLASSIFICATION OF ABSTRACT		20. LIMITATION OF ABSTRACT	

Characterization of the One Step Polyimide Synthesis

Garland Jen, S.J. Huang, and C.S.P. Sung
Institute of Materials Science
Department of Chemistry
University of Connecticut
Storrs, CT 06269-3136

Introduction

High temperature heterocyclic polymers, in particular polyimides are based on the reaction of dianhydrides with diamines. Common methods of synthesizing these materials are thermal and chemical imidization. A simple one step thermal method, consisting of a high boiling solvent such as *m*-cresol can be used to aid in the imidization process, bypassing the isolation of the polyamic acid. To take advantage of this process, it is necessary to examine the kinetics and mechanisms of these reactions.

There have been numerous studies reported for the imidization process from the precursor polyamic acid to the polyimide in a variety of solvents¹⁻⁵. However, there have been only few reports on the one step process^{6,7}.

The objectives of this research were to delineate possible mechanism and the kinetics from the reaction of 3,3',4,4'-benzophenonetetracarboxylic dianhydride (BTDA) and 1,5-naphthyl diamine (DAN) in *m*-cresol and to estimate the composition of various components which occur throughout the reaction. Model compounds were used to elucidate the compositions at various times. The reaction was monitored using UV-Visible, fluorescence, and Fourier Transform Infrared (FT-IR) spectroscopy. The conclusions from this study provide a basis for understanding the imidization chemistry in acidic solvents. From this understanding, the optimum processing conditions for the synthesis of polyimides can be made.

Experimental

The polymerization was carried out using a stoichiometric mixture of BTDA and DAN in *m*-cresol to yield a 1 wt% reaction solution, under an argon atmosphere, at 210°C. Aliquots were taken at various time intervals and diluted into NMP for UV-Vis and fluorescence analyses via Perkin-Elmer Lambda 6 and Perkin-Elmer MPF66 spectrometers, respectively. Reaction aliquots were analyzed by Infrared using a Mattson Cygnus 100 spectrometer with a resolution of 4 cm⁻¹.

Analogous solutions were made using NMP as the reaction solvent, either with or without the addition of 10% *m*-cresol to the system at temperatures of 25, 30, and 45°C. Aliquots were also taken and analyzed by UV-Vis and fluorescence. Infrared studies were accomplished with a liquid cell sample holder equipped with a temperature controller for in situ analyses of the reaction.

Results and Discussion

Figure 1 represents the overall blue shift of the reaction analyzed during the reaction process. We can see that as the reaction progresses, the absorbing peaks shifts to shorter wavelengths due to an electron withdrawing effect on the amino group of the DAN species. As the reaction proceeds, imide formation would lead to the farthest blue shift, or shortest wavelength due to the high content of carbonyl linkages, causing an extensive electron withdrawing effect. The amic acid formation is seen at 15 mins as confirmed by deconvolution of the peak by using model compound, diamic acid made from trimellitic anhydride and DAN. After the reaction was complete, the spectrum taken revealed a composition of 90% imide as compared by deconvolution and

independently confirmed by the FT-IR analysis. At the later stages of the reaction, the percentage of imide as determined by UV deconvolution and by Infrared seemed to be in good agreement as seen in Table 1. In the fluorescence analysis, the species that was monitored was DAN since all other species, especially BTDA have no appreciable fluorescence. The fluorescence emission spectra exhibits spectral changes early in the reaction. An increase and then a decrease in fluorescence intensity of the DAN species was evident. This indicates that the diamine species is complexed initially and upon reaction time, is freed or dissociated to show fluorescence intensity. At about 15 mins, the intensity reached a maximum of 9.4% DAN species present. Later in the reaction, the fluorescence emission from DAN was no longer observed, indicating that the DAN has reacted.

To alleviate the fast kinetics occurring at high temperatures, and to observe the effect of a weak acid, low temperature studies were performed on reactions in which 10% *m*-cresol was added. Infrared studies revealed polyamic acid formation for the reaction of BTDA and DAN at temperatures such as 25, 30, and 45°C. In addition, imide formation was also evident as indicated by the characteristic C-N absorption at ~1345 cm⁻¹ as seen in Figure 2. Controlled experiments in 100% NMP, exhibited amic acid formation, but no imide. These doped experiments seemed to inhibit the rate of BTDA disappearance as compared to the controls as shown in Figure 3. This would suggest some interaction of the acid with either the diamine or the dianhydride. This was evidenced by the salt formation detected for the amine with the *m*-cresol. The weak acid contains a proton which is able to donate to the amine group. This type of complexation would inhibit the reaction with the anhydride, since a nucleophile is necessary to attack the anhydride carbonyl. It is speculated that once the polyamic acid is formed, the weak acid is able to aid in the imidization step. This is a possible explanation for the imide formation seen in IR at such low temperatures. Using classical second order kinetics, the rate constants for the amidation step can be determined. For the reactions containing *m*-cresol, kinetic expressions for a consecutive reaction consisting of a second order reaction followed by a first order behavior was used. Table 2 summarizes these results and illustrates the apparent rate constants (k_1) for the formation of polyamic acid to increase with temperature and to be slower in the *m*-cresol doped cases. UV-Vis spectroscopy confirmed reaction conversion as seen by blue shifts from the reactant component, DAN (λ_s at 340 & 350nm). Fluorescence studies revealed a gradual depletion of the DAN species as the reaction time was increased.

Summary

It has been shown that the one step high temperature reaction is complex and reveals many interesting features with the use of *m*-cresol as the reaction solvent. The results have shown that UV-Visible spectroscopy can be used to monitor the wavelength shift from the diamine to the polyamic acid to the polyimide. Compositional analysis by Infrared for later stages in the reaction showed good agreement with the UV deconvolution. The conversion of the diamine was also monitored by fluorescence which revealed an initial complexation of the diamine indicative of the absence of fluorescence intensity. Upon reaction time, free diamine was detected to a maximum of 9.4%. This technique shows the sensitivity of detecting diamine in the reaction vessel.

Due to the complexity of this system, it is necessary to determine the nature of the acid, *m*-cresol with respect to the reactants. At low temperatures using an in situ method, FT-IR revealed that when 10% *m*-cresol was added to the reaction in NMP, the rate of anhydride disappearance was slower than without *m*-cresol. It has also been shown by IR analysis that imide formation and salt formation were occurring even at low temperatures. UV-Vis analysis of analogous reactions showed blue shifts and double peak maxima as the reaction progressed, supporting the trends observed by IR studies.

Overall, these spectroscopic techniques have so far provided new insight to the understanding of this complex system

Acknowledgement

This work was funded through NASA Langley Research Fellowship, NGT-70214, the Office of Naval Research and the Army Research Office (Contract No. DAAL03-92-G-0267), and the National Science Foundation, Polymers Program (Grant No. DMR 91-08060).

References

1. Dickinson, P.; Sung, C.S.P. *Macromolecules*, **25**, 3758(1992).
2. Kailani, M.; Sung, C.S.P. *Macromolecules*, **25**, 3751 (1992).
3. Kudryavtsev, V.V.; Koton, M.M.; Meleshka, T.K. Sklizkova, V.P. *Polym. Sci. USSR*, **17**, 2029 (1975).
4. Grenier-Loustalot, M.F.; Joubert, F.; Grenier, P. *J. Polym. Sci. A*, **29**, 1649 (1991).
5. Nechayev, P.P.; Vygodskii, Ya.S.; Zaikov, G.Ye.; Vinogradova, S.V. *Polym. Sci. USSR*, **18**, 1903 (1976).
6. Vinogradova, S.V.; Vygodskii, Ya.S.; Korshak, V.V. *Polym. Sci. USSR*, **12**, 2254 (1970).
7. Gerashchenko, Z.V.; Vygodskii, Ya.S.; Slonimskii, G.L.; Askaskii, A.A.; Papkov, V.S.; Vinogradova, S.V.; Dashevskii, V.G.; Klimova, V.A.; Sherman, F.B.; Korshak V.V. *Polym. Sci. USSR*, **15**, 1927 (1973).

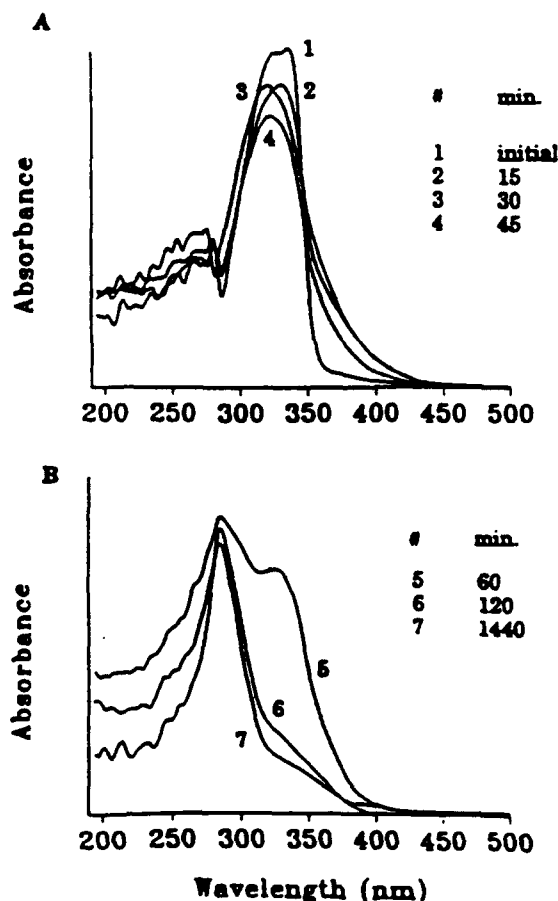


Figure 1 UV-Visible spectral changes for the reaction of DAN and BTDA at 210°C in *m*-cresol.

Table 1 Percentage of imide as determined by UV deconvolution and by infrared for the reaction at 210°C in *m*-cresol

Time (min)	UV deconvolution	Infrared
60	40	33
90	80	84
120	90	84
1440	90	85
1500	90	95

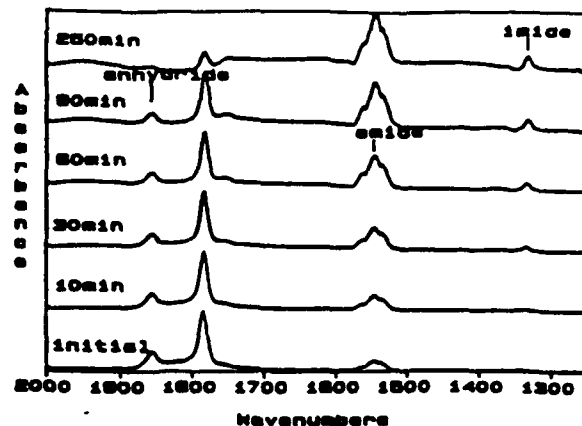


Figure 2 FT-IR spectra of amide and imide formation for the reaction of BTDA & DAN in NMP with 10% *m*-cresol at 25°C.

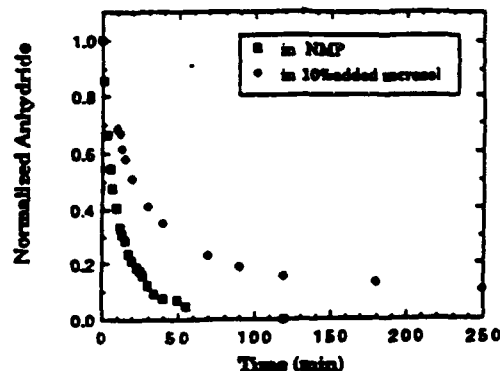


Figure 3 Anhydride disappearance as a function of reaction time of BTDA & DAN at 25°C with or without *m*-cresol added.

Table 2 Apparent rate constants for the imidization reaction under various conditions.

	25°C	30°C	45°C
In NMP			
$K_1(M^{-1}min^{-1})$	5	5	16
$E_a(Kcal/mole)$	12		
In NMP w/ 10% <i>m</i> -cresol			
$K_1(M^{-1}min^{-1})$	0.9	1	4
$E_a(Kcal/mole)$	14		
$K_2(min^{-1} \times 10^{-3})$	6	29	28

K_1 : for the formation of polyamic acid

K_2 : for the formation of imide

E_a : activation energy

codes
Serial and/or
Special

A-1